REPORT DOCUMENTATION PAGE

AD-A231 291

1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE 1-23-91	3. REPORT TYPE AND DATES COVERED Quarterly Tech. 9/12/90 - 12/11/90

4. TITLE AND SUBTITLE	5. FUNDING NUMBERS
Distortion-Free X-Ray Mask Technology	N00014-90-K-2018
6. AUTHOR(S) Prof. Henry I. Smith	68-1748-90

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)	8. PERFORMING ORGANIZATION REPORT NUMBER
Research Laboratory of Electronics Massachusetts Institute of Technology 77 Massachusetts Avenue Cambridge, MA 02139	

9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES)	10. SPONSORING / MONITORING AGENCY REPORT NUMBER
Naval Research Laboratory 4555 Overlook Avenue, SW Washington, DC 20375	

11. SUPPLEMENTARY NOTES

The view, opinions and/or findings contained in this report are those of the author(s) and should not be construed as an official Department of the Army position, policy, or decision, unless so designated by other documentation.

12a. DISTRIBUTION / AVAILABILITY STATEMENT	12b. DISTRIBUTION CODE
Approved for public release; distribution unlimited.	

13. ABSTRACT (Maximum 200 words)

Work by Prof. Smith and his collaborators is summarized here

DTIC
ELECTE
JAN 29 1991
S D
D

14. SUBJECT TERMS			15. NUMBER OF PAGES 4
			16. PRICE CODE

17. SECURITY CLASSIFICATION OF REPORT	18. SECURITY CLASSIFICATION OF THIS PAGE	19. SECURITY CLASSIFICATION OF ABSTRACT	20. LIMITATION OF ABSTRACT
UNCLASSIFIED	UNCLASSIFIED	UNCLASSIFIED	UL

91 1 28 100

Distortion-Free X-Ray Mask Technology

Quarterly Technical Report
for the period
September 12, 1990 to December 11, 1990

by
Research Laboratory of Electronics
Massachusetts Institute of Technology
Cambridge, MA 02139

Accesion For

NTIS	CRA&I	✓
DTIC	TAB	
Unannounced		
Justification		

By

Distribution /

Availability

Dist

A-1

Principal Investigator

Prof. Henry I. Smith
Dept. of Electrical Engineering and Computer Science
Massachusetts Institute of Technology

January 11, 1991

Objective:

The objective of this research project is to develop a closed-loop, feedback-controlled, robust system for reliably achieving zero stress in tungsten (W) films sputtered onto various x-ray mask membranes, and to transfer the technology to the National X-ray mask shop. Our system for controlling stress in sputtered W films is based on the measurement of resonant frequency. Since resonant frequency depends on both the thickness and the stress of the W films, if the thickness is known, the stress is easily calculated from

$$V_{res} = A \left[\frac{B + \sigma_w t_w}{C + D t_w} \right]^{1/2}$$

where A, B, C and D are constants, known in advance, σ_w is the tungsten stress and t_w is the W thickness.

Progress:

1. We have made a major improvement in the software that is used in the in-situ stress monitoring system. A LABVIEW II program from National Instruments is used to replace the original C program. This program is chosen to facilitate the interface between the operator and the MacII computer during the sputtering process. Figure 1 shows the front panel displayed during the deposition process. On the bottom left side of the panel is all the data required to describe the membrane properties (e.g. density, radius, initial stress, and thermal expansion coefficient) that are required for the computation of an empirical curve that we will try to follow during the

Fig. 1
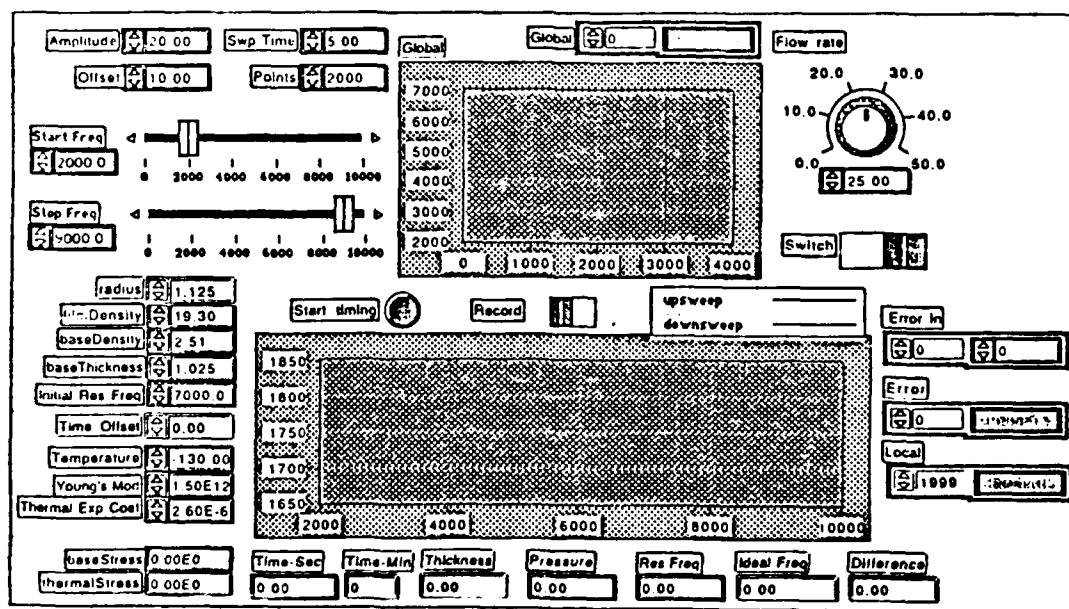
deposition process. On the top left side of the display is the control panel for the function generator that we use to drive the membrane. Here we can specify the sweeping frequency range, driving amplitude, and number of data points to be collected for each frequency sweep. On the bottom of the display is a graphical display of the membrane response to the frequency sweep, and all the data extracted or measured for that particular time interval of data collection (i.e. the measured resonant frequency, the calculated resonant frequency, sputtering pressure and deposited W film thickness). On top of this graphical display is the resonant frequency of the membrane measured for the entire time interval of the sputtering process. Finally, at the top right of the display is the control panel for the mass flow controller, which allows direct setting of Ar flow rate into the sputtering chamber and therefore control of sputtering pressure.

2.   We are in the process of doing extensive testing on the data acquisition and control program that we have written using LABVIEW II. Some initial results that we obtained are very encouraging. Figure 2(a-c) depict three different sputtering runs that shows the stress control with the in-situ set-up, by making the resonant frequency follow (or oscillate about) an empirically calculated curve. All three cases gave zero stress (i.e. $<5 \times 10^7$ dynes/cm^2). The solid points are experimental measurements of the resonant frequency, and the solid curve is the calculated curve that the experimental measurements should fall on in order to maintain zero stress throughout the deposition.
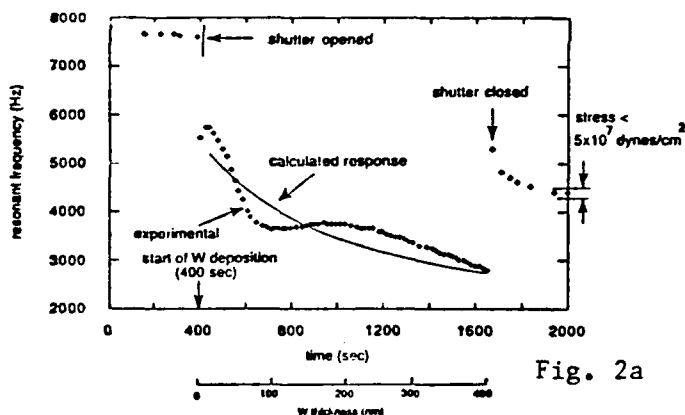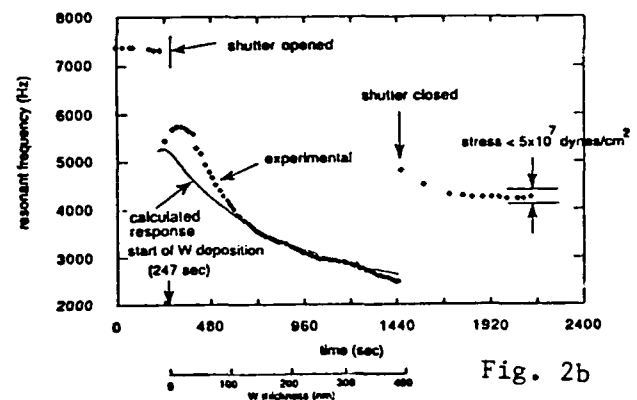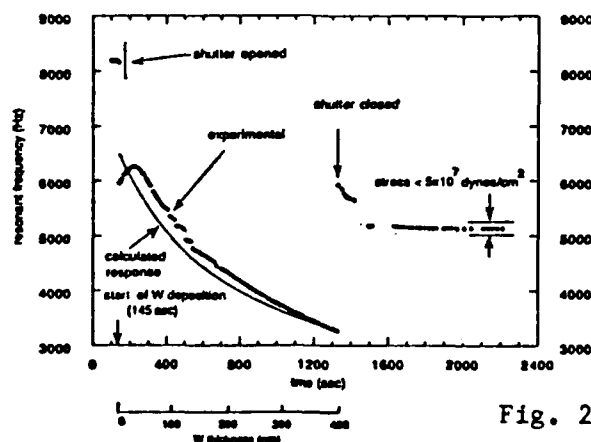

Fig. 2a

Fig. 2b

Fig. 2c

Note in Fig. 2a that the resonant frequency of the membrane is constant at 7800 Hz prior to opening the shutter and commencing the W deposition. As soon as the shutter is opened, the resonant frequency decreases by ~2kHz and then rises and settles down to follow the shape of the ideal curve after about 120 sec. We attribute this transient behavior to heating of the membrane. Because it is only 1 μm thick the membrane heats up rapidly once it is exposed to the plasma. This causes the sudden drop in resonant frequency. The corresponding change in stress is given by

$$\Delta\sigma = -\alpha_m \, E_m \, \Delta T$$

where ΔT is the difference in temperature between the membrane and the more massive supporting substrate, α_m is the coefficient of thermal expansion of the membrane, and E_m is Young's modules. For a Si membrane ($\alpha = 2.6\times10^{-6}\,K^{-1}$, $E = 1.6\times10^{-12}$ dynes/cm^2). A drop of 2kHz corresponds to a $\Delta\sigma$ of 5-6x10^8 dynes/cm^2. This corresponds to a ΔT of 120-140°C, which is about the expected temperature rise based on the power input to the membrane and the thermal conduction. The slower (~ 100 sec) rise is resonant frequency after the rapid initial drop is attributed to heating of the supporting substrate around the perimeter of the membrane which reduces the temperature gradient ΔT, causing some of the membrane stress to be restored. Note that this transient behavior (rapid shift of ~ 2kHz followed by a slower shift in the opposite direction of < 1kHz) is repeated at the end of the sputtering run, as it should be. That is, the membrane also cools much more rapidly than the supporting substrate.

3.   *We have improved the RIE of tungsten by using new gas combinations* of CHF$_3$/SF$_6$ that are mixed at a flow ratio of 1.8-2.3:1 at a bias voltage of 600V, a pressure of 10mtorr, and power density of 0.41 w/cm^2. Figure 3 show the etch rate variation as we slowly increase the SF$_6$ flow rate in CHF$_3$.

Etch rate vs SF$_6$/CHF$_3$ gas mixtures

Fig. 3
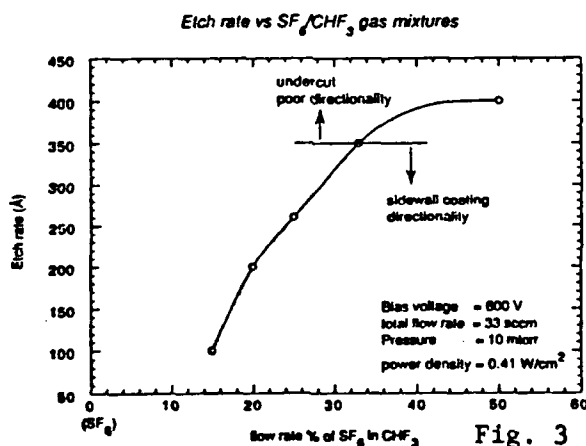
Summary:

In summary, we have passed our scheduled milestones; our progress is ahead of schedule.

NAVAL RESEARCH LABORATORY

DISTRIBUTION LIST

Dr. Martin Peckerar
Scientific Officer   4 copies

Code: N00173
Naval Research Laboratory
4555 Overlook Avenue, S.W.
Washington, DC 20375

Administrative Contracting Officer   1 copy
E19-628
Massachusetts Institute of Technology
Cambridge, MA 02139

Director   6 copies
Naval Research Laboratory
Washington, DC 20375
Attn: Code 2627

Defense Technical Information Center   2 copies
Bldg. 5, Cameron Station
Alexandria, VA 22314